

# Specimen size and shape effects on strength of concrete in the absence and presence of steel fibers

**Ali Mardani-Aghabaglou** (Main and Corresponding Author)

Bursa Uludag University  
16000, Bursa (Turkey)  
alimardani@uludag.edu.tr

**Sultan Husein Bayqra**

Bursa Uludag University  
16000, Bursa (Turkey)  
sultanhuseinbayqra@yahoo.com

**Amir Nobakhtjoo**

Istanbul Technical University  
16000, Bursa (Turkey)  
nobakhtjoo.amir@gmail.com

**Manuscript Code:** 15450

**Date of Acceptance/Reception:** 21.03.2021/17.06.2020

**DOI:** 10.7764/RDLC.20.1.128

## Abstract

In this research, the effects of size and shape on compressive and splitting tensile strength of fibrous and non-fibrous concrete specimens with different characteristic strength were investigated. With this aim, both fibrous and non-fibrous 10 different concrete mixtures with 0.3, 0.4, 0.5, 0.6 and 0.7 Water/Cement ratio were prepared. In the fibrous mixture specimens, the total amount of steel fibers to 1% by total volume. In the entire specimens, 42.5 R type Portland cement were used as bonding elements while crushed lime stones in 3 sizes were added to the mixtures. Furthermore, to evaluate the influence of size and shapes over specimens' strength, for each concrete mixtures two 10 cm and 15 cm cubic specimen beside two 10×20 cm and 15×30 cm cylindrical specimens were prepared as well. The prepared specimens were subjected to compressive and splitting tensile tests. The results showed that, regardless of the fiber amount and specimens' shapes, the decrease in specimens' size resulted in higher strength. But in the high ratio of Water/Cement and fibrous mixtures, the mentioned behavior was not observed.

**Keywords:** shape effect, size effect, steel-reinforced concrete, splitting tensile strength, compressive strength.

## Introduction

The fact that the concrete holds heterogenic texture results in different stress values in the case of loading as a result of hydration and hardening of its components. Due to the external and internal effects, significant stresses occur especially on the aggregate-cement paste interface (transition zone), known as the weakest part of the concrete (Mardani-Aghabaglou et al., 2019). These stresses result in cracks on the aggregate-cement paste surface. Along with the effects of external stresses, these cracks grow and affect the mechanical properties and stress-strain behavior of the concrete negatively. One of the most preferred methods to improve these properties in concrete is the addition of steel fiber in concrete mixtures (Alex & Arunachalam, 2019; Ouedraogo et al., 2021). These randomly distributed fibers increase the occupancy and limit the cracks at different stages of the concrete, preventing their growth and distribution of the internal stresses. These favorable effect of the fibers alter the fracture behavior of the concrete after maximum load positively. The effectiveness of the steel fibers used in concrete might change in accordance with fiber geometric structure, fiber type, aspect ratio, tensile strength, and volume (Köroglu & Ashour, 2019; Zeynal, 2008).

As it is known, compressive and tensile strengths are two important parameters for defining the mechanical properties of the concrete. The checking of compressive strength of concrete is commonly essential during the structural design. Besides, controlling of the tensile strength is important in particular structures such as earthquake resistant structures, airstrip, and pavement. The compressive strengths of the standard cylinder and cube specimens (15 × 30 cm, 15 cm) can be considered as common feature used in concrete quality control. As a known fact that the compressive strength of concrete varies according to the shape and size of the concrete specimens. The shape and size of the specimens used to determine the strength of concrete are not the same in every country; however, the most preferred are cube and cylinder specimens. That is, cube specimens (15 cm) are used in Germany, UK and many other European countries while cylinder specimens (15 × 30 cm) are used in the USA, Canada, South Korea, Australia and France. Also, both cylinder and cube specimens are used in many countries (e.g. Norway). Cylinder and cube strengths obtained from the same concrete mixer may differ due to specimens' shape and size (Yi et al., 2006).

It is commonly known that the cube specimens show higher compressive strength than the cylindrical specimens because of their end effects (Aslani, 2013; Felekoğlu & Türkel, 2005). However, some researchers reported that the strength difference is less in high-strength concretes (Yi et al., 2006). Many studies in this field have been conducted since the early 1900s (Aitcin et al., 1994; Neville A.M, 1996; Tokyay & Özdemir, 1997; Che et al., 2011; Dehestani et al., 2014; Li et al., 2018; Khalilpour & Dehestani, 2021; Zhang et al., 2021). Many researchers have tried to develop a suggestion to convert non-standard concrete specimens to standard specimens. The relation between the strength of cylinder and cube specimens were investigated in many studies (Gyurkó & Nemes, 2020; Li et al., 2018). It is a common use that the strength of the cylinder specimen to be multiplied by a coefficient of 1.2 in order to be converted into the cube specimen strength. However, this coefficient decreases with increasing concrete strength. According to fib MC 2010 (CEB-FIP MC10, 2010) increasing the compressive strength of concrete causes the cube-cylinder strength ratio to decrease gradually from 1.25 to 1.15. While 1.25 ratio has 40 MPa cylinder compressive strength and 1.15 ratio corresponds to 100 MPa.

Del Viso et al., (2008) investigated the effects of the size and shape of the cylindrical and cube specimens at different sizes on the compressive strength of high strength concrete. As a result, it has been seen that the small specimens showed high compressive strengths. The size effect was reported to be less in cylinder specimens than in cube specimens. (Dehestani et al., (2014) in their study on self-consolidating concrete (SCC), investigated the effects of specimen size and shape on the compressive strength. Cylinder and cube specimens were used in the study. Regardless of the aspect ratio, it was found that the concrete strength decreased as the specimen size increased and the decrease was more obvious in the specimens with low aspect ratio. Strength ratio decrease for the cylindrical specimens were observed with the decrease of the aspect ratio. According to these results, the specimen size was found to be more distinct in specimens with low aspect ratio. It was stated that the decrease in strength ratio at stable aspect ratio is mostly dependent on the mixing ratios, especially the W/C ratio of the mixture.

It was also described that the specimen size is even more distinct in low strength concretes. It was found that the specimen size effect at high aspect ratios ( $h / d$ ) became independent from water cement ratio. Moreover, the cube specimens showed higher strength than cylindrical specimens when the slenderness ratios are the same. (Gyurkó & Nemes, (2020) examined the effect of sample size and shape on the compressive strength of normal strength concrete. The results showed that the size effect was stronger in low-strength concretes due to the mixtures' inhomogeneity. It was also explained that the size effect was more pronounced in cubic samples than in cylindrical samples.

### **Novelty, scope, and significance**

As a result of the conducted researches, it can be stated that the effect of specimen's shape and size on concrete strength has been investigated. These studies revealed different correlation coefficients on specimens' shape and size. However, it has been determined that there is a lack of studies to investigate the effect of sample shape and size in fiber concretes with different W/C ratios and to establish correlation coefficients between these samples. This study investigates the effect of sample shape and size on the strength of steel fibrous concretes with different W/C ratios. For this purpose, fibrous and non-fibrous concrete mixtures with five different W/C ratios, 0.3, 0.4, 0.5, 0.6 and 0.7, were produced. In fibrous mixtures, 1% steel fiber with an aspect ratio of 64 the total volume was used. To determine the specimen shape and size effects on concrete strength, 10 cm and 15 cm cube specimens, 10 × 20 cm, and 15 × 30 cm cylinder specimens were prepared. Thus, 480 cylindrical and cubic specimens were produced in total and strength-time and strength-specimen size and shape relationships were compared in fibrous and non-fibrous concretes with different strength classes.

## Materials and methods

In this part, the chemical and physical properties of the materials used in the experimental study and the amounts of materials used for the production of 1 m<sup>3</sup> concrete are demonstrated. In order to minimize the effect of the ambient conditions on the experiment, all the materials which are used in the study were kept in a room with a temperature of 20 ± 2 °C for 48 hours before the experiment.

### Cement

In the experimental studies, CEM I 42.5R type cement produced by Bursa cement factory with 3530 cm<sup>3</sup> / g of specific surface and 3.15 of specific weight, respectively, were used in accordance with TS EN 197-1 (TS EN 197-1, 2012) Standard. The mechanical, physical and chemical properties of the cement used are given in Table 1.

**Table 1.** Chemical composition and mechanical and physical properties of the cement. (Self-Elaboration).

Item	(%)	Physical Properties		
SiO <sup>2</sup>	18.86	Specific Gravity		3.15
Al <sup>2</sup> O <sup>3</sup>	5.71	Mechanical Propierties		
Fe <sup>2</sup> O <sup>3</sup>	3.09	Compressive	1-Day	14.7
CaO	62.70	strength (MPa)	2-Day	26.80
MgO	1.16		7-Day	49.80
SO <sup>3</sup>	2.39		28-Day	58.5
Na <sub>2</sub> O+0.658K <sub>2</sub> O	0.92	Fineness		
Cl <sup>-</sup>	0.01	Blaine Specific surface (cm <sup>2</sup> /g)		3530
Insoluble residual	0.32	Residual on 0.045 mm sieve (%)		7.6
Loss on ignition	3.20			
Free CaO	1.26			

### Aggregates

In concrete mixtures crushed limestone aggregate with the largest grain diameter of 22 mm was used. Water absorption capacity and specific gravity of aggregates obtained according to TS EN 1097-6 (TS EN 1097-6, 2013) Standard is given in Table 2. In addition, gradation of the aggregates shown in Table 3 was performed according to TS EN 206 (TS EN 206, 2014) Standard. In concrete mixtures, crushed limestone aggregate as 40% of total aggregate volume of 0-5 mm, 30% of 5-12 mm and 30% of 12-22 mm of size was used.

**Table 2.** Physical properties of the aggregates used in the concrete mixtures. (Self-Elaboration).

Aggregate				
Type	Dimension (mm)	Specific Gravity	Bulk Density (kg/m <sup>3</sup> )	Water Absorption Capacity (%)
Crushed limestone	0-5	2.72	1655	0.80
	5-12	2.68	1441	0.44
	12-22	2.71	1405	0.24

**Table 3.** Sieve analysis of the aggregates used in the mixtures. (Self-Elaboration).

Sieve size (mm)	0-5 mm	5-12 mm	12-22 mm
31.5	100	100	100
16	100	100	49.7
8	100	72.2	0.1
4	100	7	0
2	77.5	0	0
1	49.3	0	0
0.5	32	0	0
0.25	12.9	0	0
0.125	2.5	0	0

## Water reducing admixtures

Polycarboxylate-ether based, high rate water reducing admixtures purchased from Polisan company were used in different ratios to provide the desired slump values in concrete mixtures. Some properties of the water reducing additives used by the manufacturer are shown in Table 4.

Table 4. Properties of the water reducing admixture. (Self-Elaboration).

Type	Density (g/cm <sup>3</sup> )	pH value	Chloride Content (%)	Alkali Content, Na <sub>2</sub> O (%)
Polycarboxylate ether based	1.023-1.063	5-8	<0.1	<10

## Steel fiber

In fibrous mixtures, mono-type steel fiber with 64 aspect ratio and two hooks at both ends in accordance with TS EN 14889-1 (TS EN 14889-1, 2006) standard was used. Additionally, for all fibrous mixtures, the fiber utilization rate was kept constant at 1% of the total mixtures volume. The mechanical and physical properties of the used steel fibers are given in Table 5.

Table 5. Mechanical and physical properties of the steel fibers. (Self-Elaboration).

Length (mm)	35
Diameter (mm)	0.55
Density (g/cm <sup>3</sup> )	7.8
Aspect ratio	64
Tensile strength (N/mm <sup>2</sup> )	1500

## Preparation of the mixtures

As previously mentioned, a set of 10 mixtures with and without fibers were produced within the extent of the study. The slump value was kept constant at  $17 \pm 2$  cm in all mixtures. The slump test was performed according to the TS EN 12350-2 (TS EN 12350-2, 2010) standard. High water reducing admixture was used in different ratios to provide requested slump value. The material quantities for 1 m<sup>3</sup> of concrete production are given in Table 6. As a result, the water reducing admixture requirement has increased with the use of fiber in order to achieve the requested slump value ( $17 \pm 2$  cm). This was more distinct in concrete with low W/C ratios. As expected, the fresh state unit weight of concrete mixtures increased slightly with the use of fiber. Concrete mixtures prepared in the mixer were placed in the molds by compaction according to the relevant standard. The produced specimens were demolding after 24 hours and kept in water with a constant temperature of  $22 \pm 2$  °C.

The control mixtures K03, K04, K05, K06, K07 and fibrous mixtures were encoded with the indications of L03, L04, L05, L06, L07.

Table 6. Mixture quantities for 1 m<sup>3</sup> concrete. (Self-Elaboration).

Mixture code	Cement (kg)	Water (kg)	Aggregate (kg)			Fiber (kg)	Chemical admixture (kg)	Slump (cm)
			0-5 (mm)	5-12 (mm)	12-22 (mm)			
K03	650	195	629	465	477	0	3.75	17
K04	488	195	686	564	513	0	2.25	18
K05	390	195	721	533	539	0	1.34	16
K06	325	195	744	550	556	0	0.74	15
K07	278.6	195	761	562	568	0	0.5	17
L03	650	195	618	457	462	78	4.5	16
L04	488	195	676	499	505	78	2.75	17
L05	390	195	710.5	525	531	78	1.75	15
L06	325	195	733.3	542	548	78	1	16
L07	278.6	195	761	562	568	78	0.52	15

### Fresh state results

In this study, the slump values and fresh state unit weights of the mixtures were measured as fresh state properties. The results are given in Figures 1 and 2.

Figure 1. Slump values of the fibrous and non-fibrous mixtures at different W/C ratios. (Self-Elaboration).


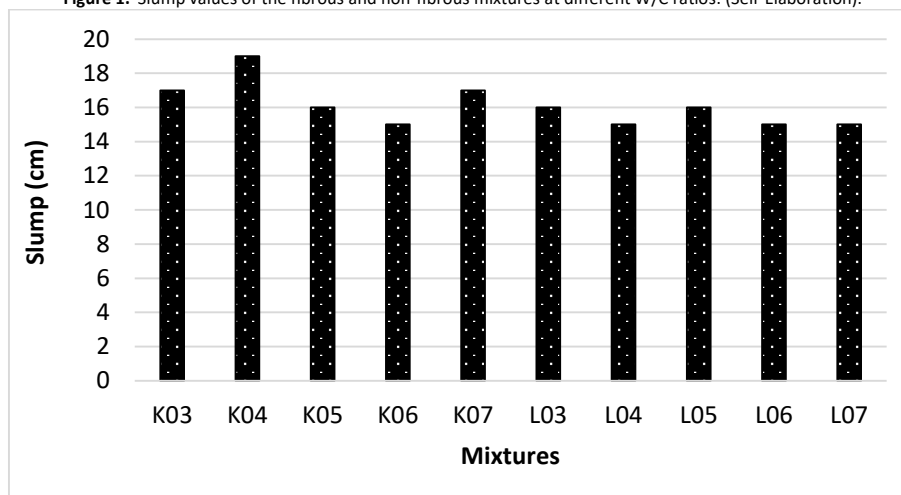


Figure 2. Unit weights of the fibrous and non-fibrous mixtures at different W / C ratios. (Self-Elaboration).

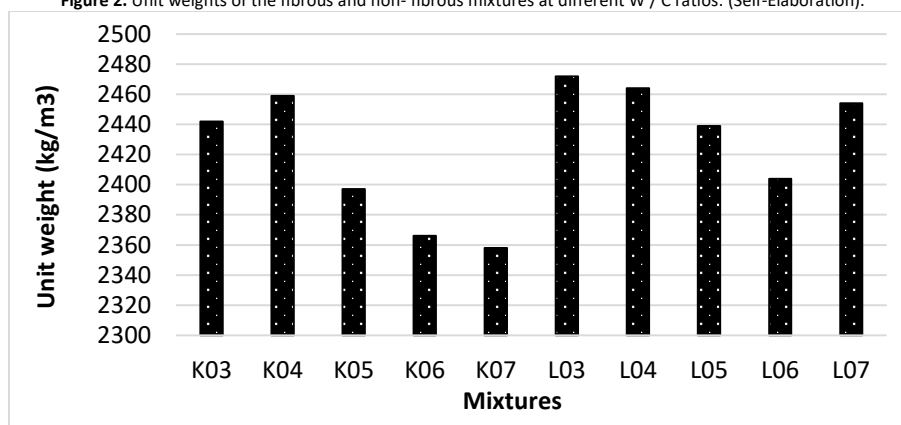

As expected, with the increase of the W/C ratio of the mixtures, the admixture demand for providing the desired slump value increased. For example, 0.5 kg water reducing admixture was used in K07 mixture to provide  $17 \pm 2$  cm whereas 3.75 kg water reducing admixture was used to increase this value by 7.50 times to provide this value in K03 mixture. The admixture requirement for providing mentioned target slump value in mixtures increased with the use of fiber. The unit weights of the mixtures increased with the decreasing of W/C ratio and the use of steel fiber, which shows that steel fiber in the mixtures was distributed in the mixture homogeneously in the fibrous mixtures.

### Hardened state results

Compressive and splitting tensile test results of concrete mixtures with different sizes and shapes are shown in Figure 3-6 for fibrous and non-fibrous cases. However, strength values could not be measured due to the wall effect of 10 cm cube and  $10 \times 20$  cm cylinder specimens containing 1% steel fiber with a W / C ratio of 0.7.

Figure 3. Compressive strength (MPa) of the non-fibrous mixtures. (Self-Elaboration).

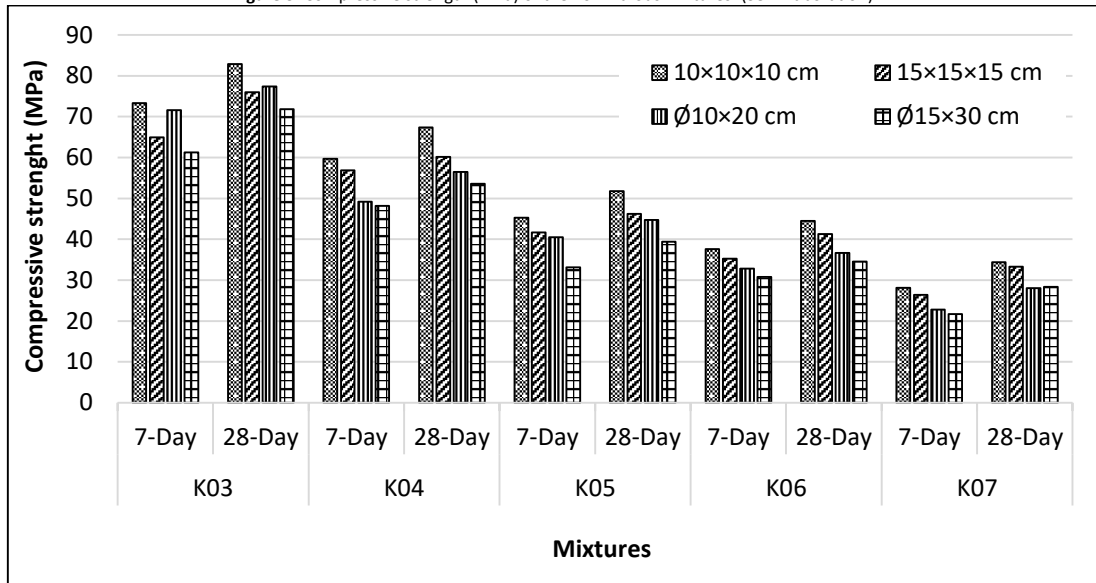


Figure 4. Compressive strength (MPa) of the mixtures containing 1% steel fiber. (Self-Elaboration).

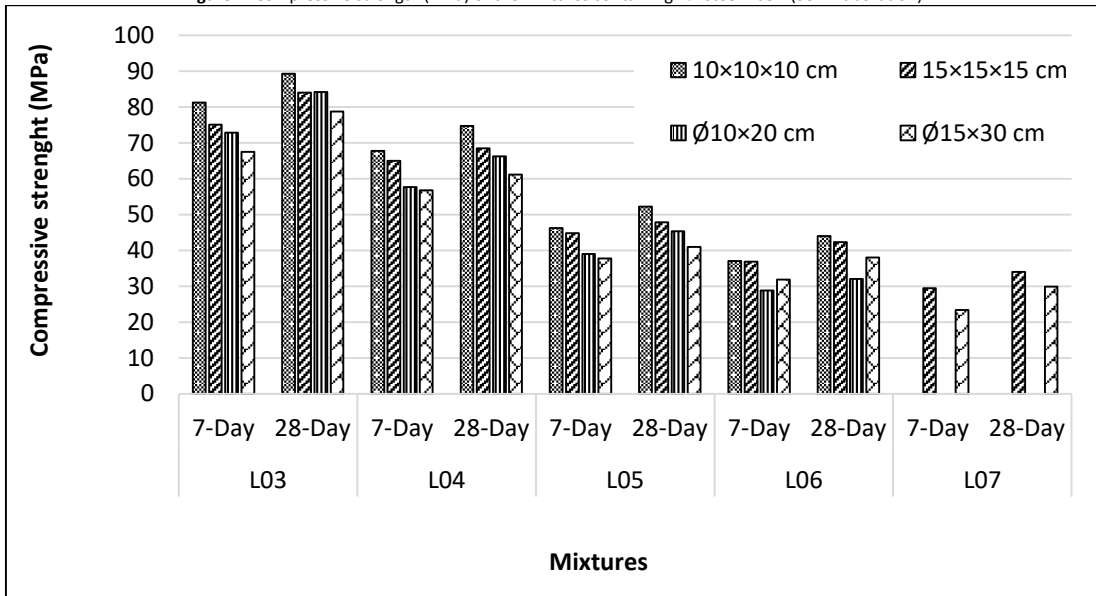


Figure 5. Splitting-tensile (MPa) strength of the non-fibrous mixtures. (Self-Elaboration).


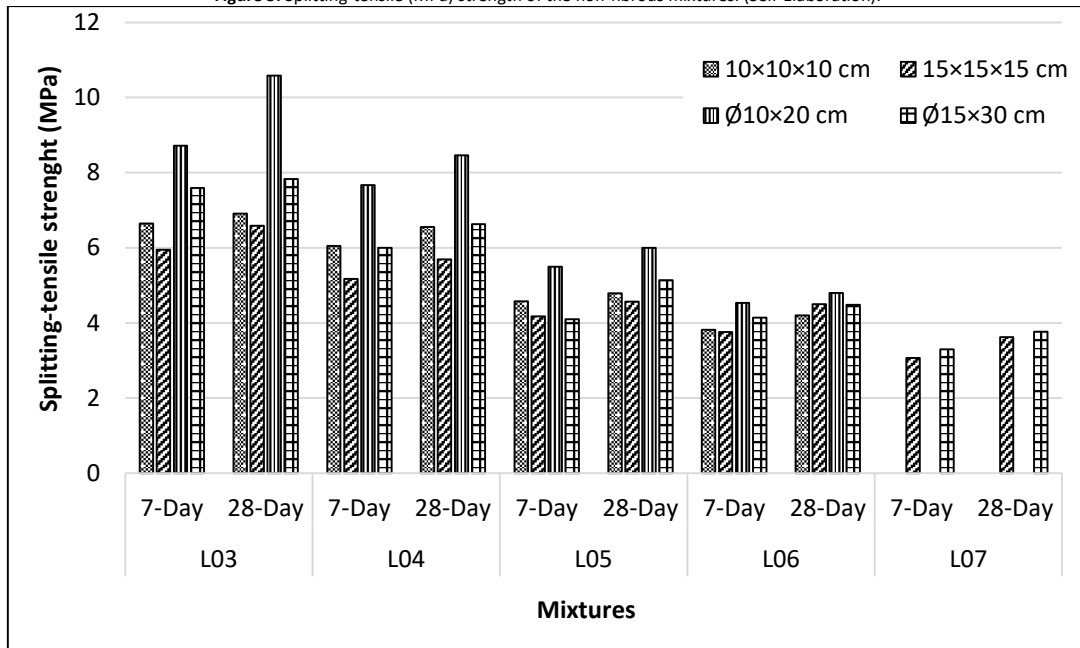


Figure 6. Splitting-tensile strength (MPa) of the mixtures containing 1% steel fiber. (Self-Elaboration).

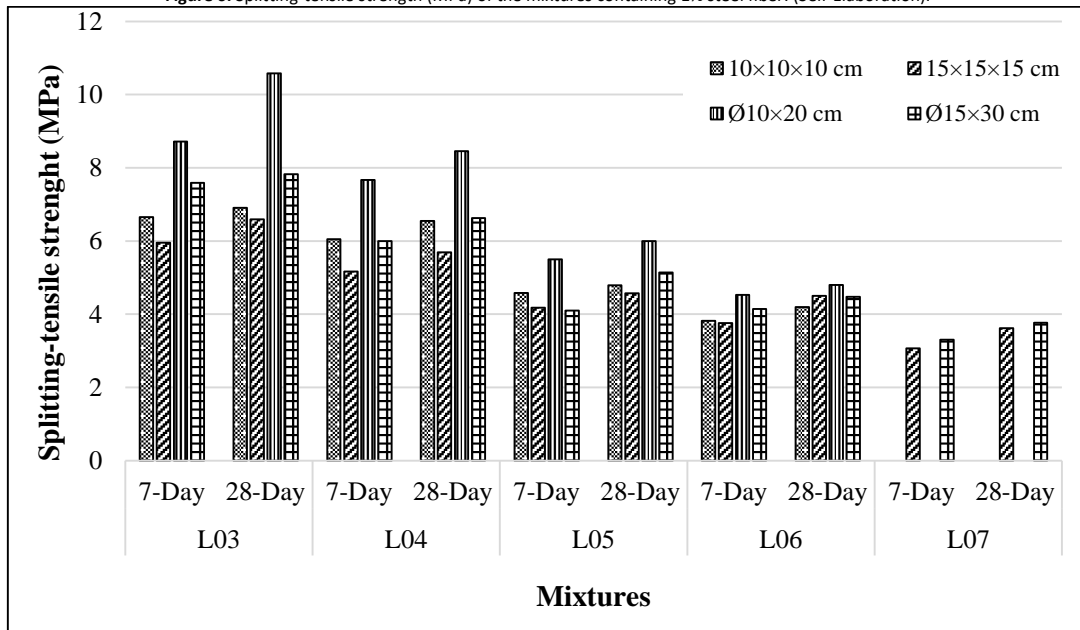

The shape of the specimens with a 0.3 W / C ratio subjected to splitting-tensile and compressive tests are shown in Figures 7 and 8, respectively.

Figure 7. Specimens subjected to the splitting-tensile test. a) Non-fiber specimen; b) Fibrous specimen. (Self-Elaboration).


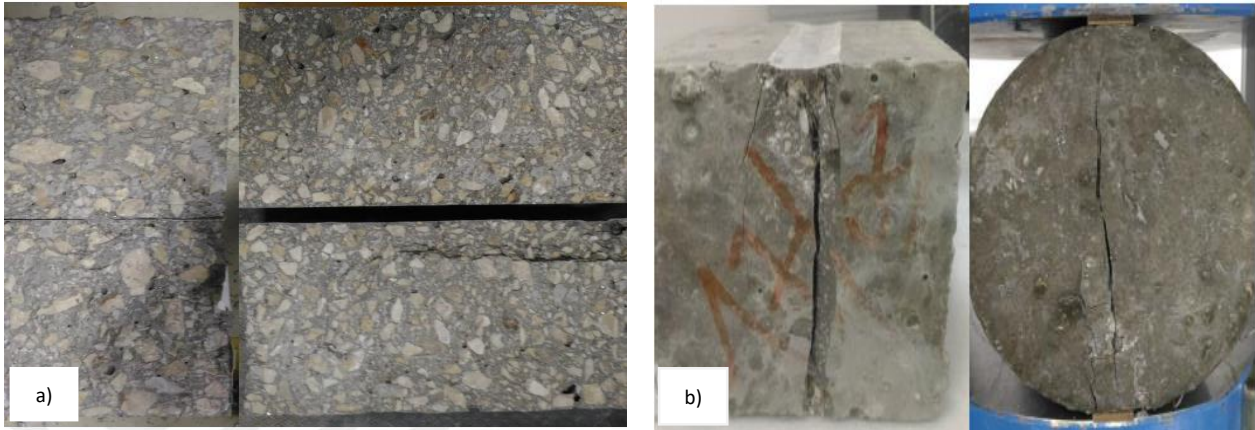


Figure 7. Specimens subjected to the compressive test. a) Non-fiber specimen; b) Fibrous specimen. (Self-Elaboration).

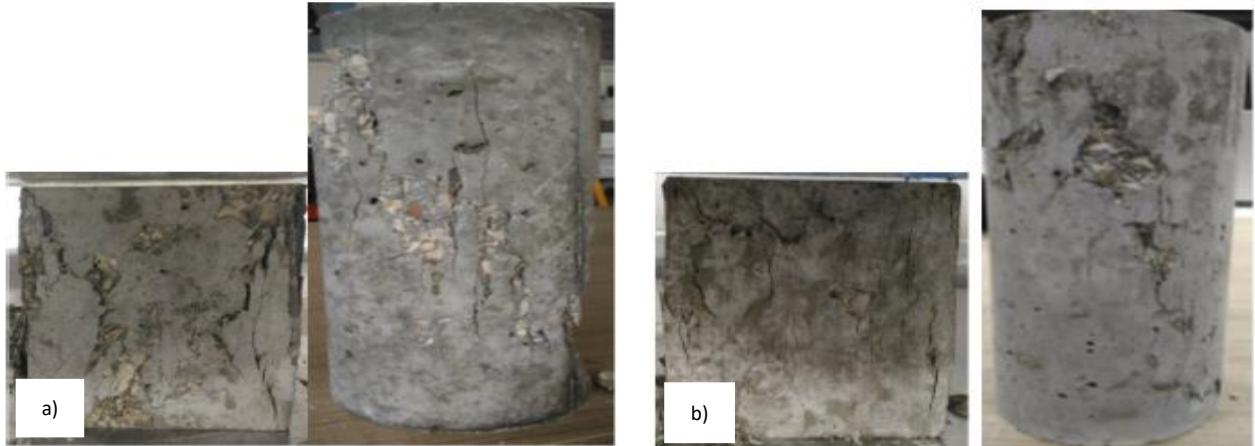

### Time-strength relationship

In order to clearly examine the effect of the time factor on the strength development of specimens with different shapes and sizes, the 7-day relative strength ratio to the 28 day-strength for each mixture is shown in Tables 7 and 8. Regardless of the specimen shape and size, the average 7-day relative strength results for different W/C ratios are given in Tables 7 and 8.

Table 7. 7-day compressive strength to 28-day compressive strength ratio for the specimens with different W / C ratio (%). (Self-Elaboration).

Mixture code	10×10×10 cm	15×15×15 cm	10×20 cm	15×30 cm	Average (%)
K03	88	85	93	85	88
K04	89	95	87	90	90
K05	87	90	91	84	88
K06	85	85	89	89	87
K07	82	79	81	77	80
L03	91	89	87	86	88
L04	91	95	87	93	91
L05	88	94	86	92	90
L06	84	87	90	84	86
L07	0	87	0	78	83



**Table 8.** 7-day splitting-tensile strength to 28-day splitting-tensile strength for the specimens with different W/ C ratio (%). (Self-Elaboration).

Mixture code	10×10×10 cm	15×15×15 cm	Ø10×20 cm	Ø15×30 cm	Average (%)
K03	92	86	89	90	89
K04	83	81	93	96	88
K05	95	94	85	83	89
K06	97	94	87	97	94
K07	92	94	86	91	91
L03	96	90	82	97	91
L04	92	91	91	90	91
L05	96	91	92	80	90
L06	91	84	94	92	90
L07	0	85	0	88	87

As known, concrete is a building material which gains strength by time as a result of the hydration. According to the results, the strengths of the concrete mixtures increased by time regardless of the specimen shape, size and fiber usage. As an expected result, strength increase rate observed to be high during the first days of the hydration and decelerates in time (Ashkari, 2015). It can be understood from Table 7 that between 80% and 90% of the average compressive strength of the concrete mixtures is provided during the first 7 days. The concrete strength change for low W/C ratio and higher strength value was faster during the first 7 days compared to the mixtures with high W/C ratios. For instance, the 7-day compressive strength of the K03 mixture with the 0.3 W/C ratio of and without steel fiber was 88% of the 28-day compressive strength. However, that ratio in K07 mixture which is prepared with 0.7 water cement ratio and without contain steel fiber is observed as 80%, as can be seen in Table 7.

This situation is resulted from the high cement content in K03 mixtures. A certain amount of cement increase results in increase of the hydration rate, thus the concrete strength gain rate advances as well. Concrete mixtures gained nearly 90% of the 28-day splitting-tensile strength during the first 7 days (Table 8). It was observed that the rate of splitting tensile strength gain of the concrete mixtures with different W/C ratio is very close to each other. Similar results were seen in 15 cm separated cube, 10×20 cm and 15×30 cm cylinder specimens as shown in Figure 3-6. Similar behaviors were also observed in fiber-containing mixtures. As a result, it can be seen that the rate of gaining strength for concrete mixtures decreases when W/C ratio reduces, which is due to the increased rate of hydration in concretes with low W/C ratio (mixtures with high cement content).

### Specimen size and shape-strength relationship

Based upon the strength of 15 cm cube specimens for each W / C ratio in fibrous and non-fibrous mixtures relative strengths of other specimens were calculated in order to determine the effects of specimen shape and size on compressive strength. The process was applied for both 7-day and 28-day specimens. Obtained results are shown in Figure 9-12.

**Figure 9.** Relative compressive strength of the non-fibrous mixtures according to 15 cm cube specimen (%). (Self-Elaboration).

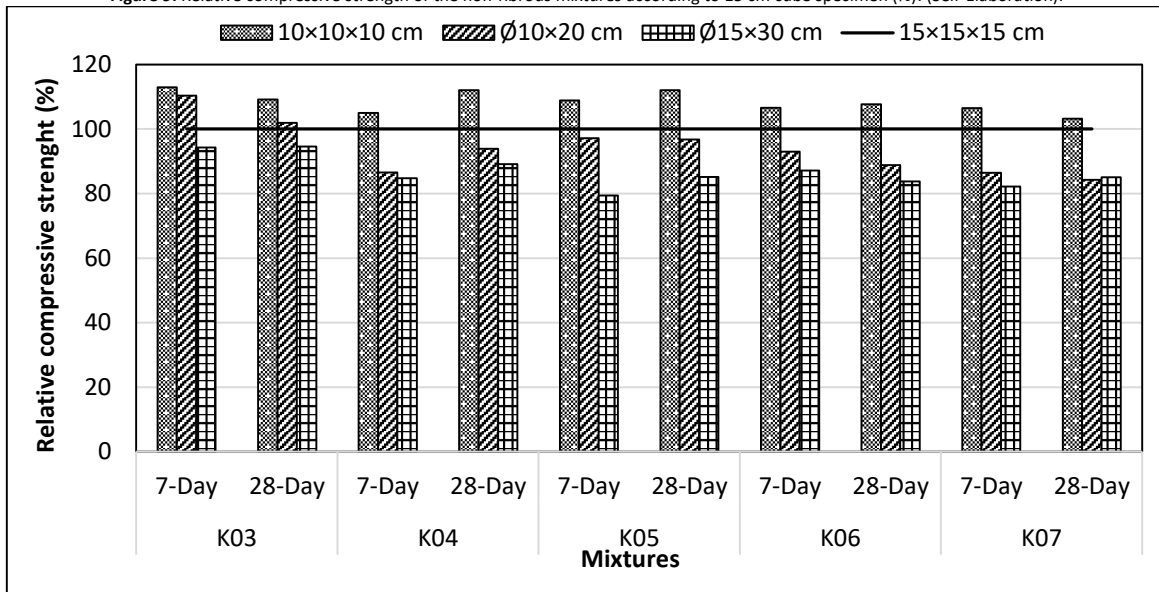


Figure 10. Relative compressive strength of the mixtures with 1% steel fiber according to 15 cm cube specimen. (Self-Elaboration).

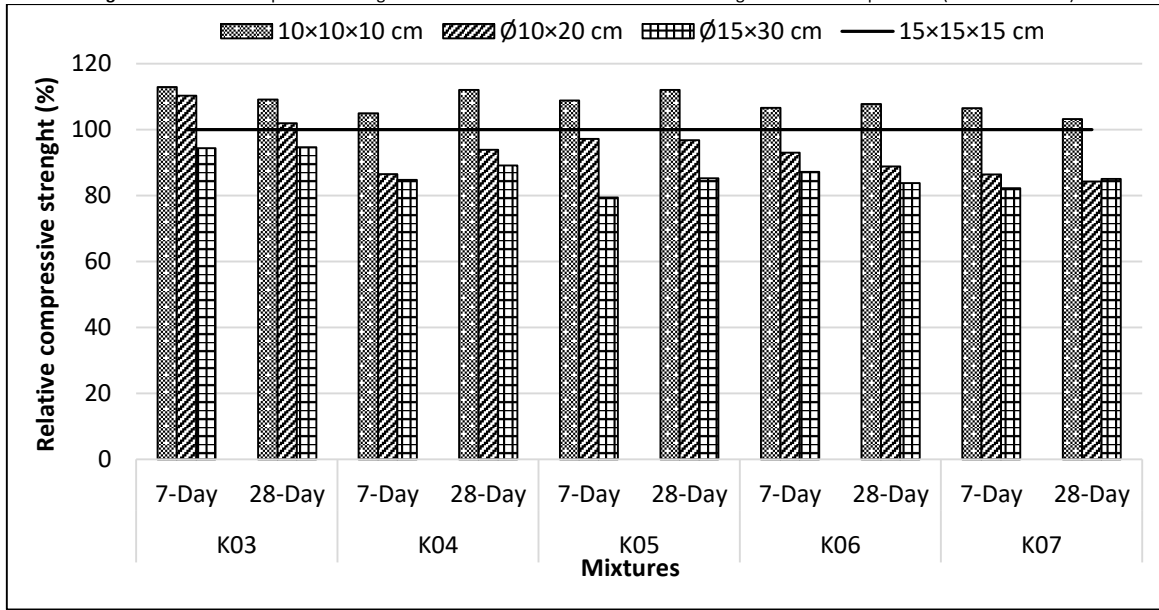


Figure 11. Relative splitting-tensile strength of the non-fibrous mixtures according to 15 cm cube specimen (%). (Self-Elaboration).


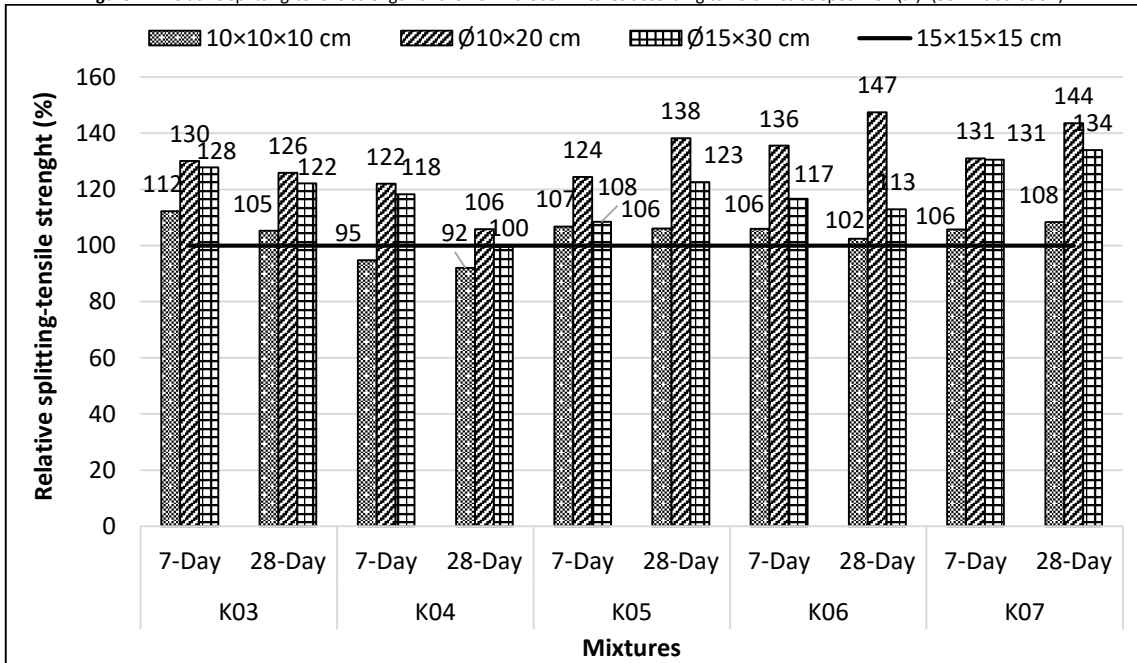


Figure 12. Relative splitting-tensile strengths of the mixtures containing 1% steel fiber according to 15 cm cube specimen (%). (Self-Elaboration)

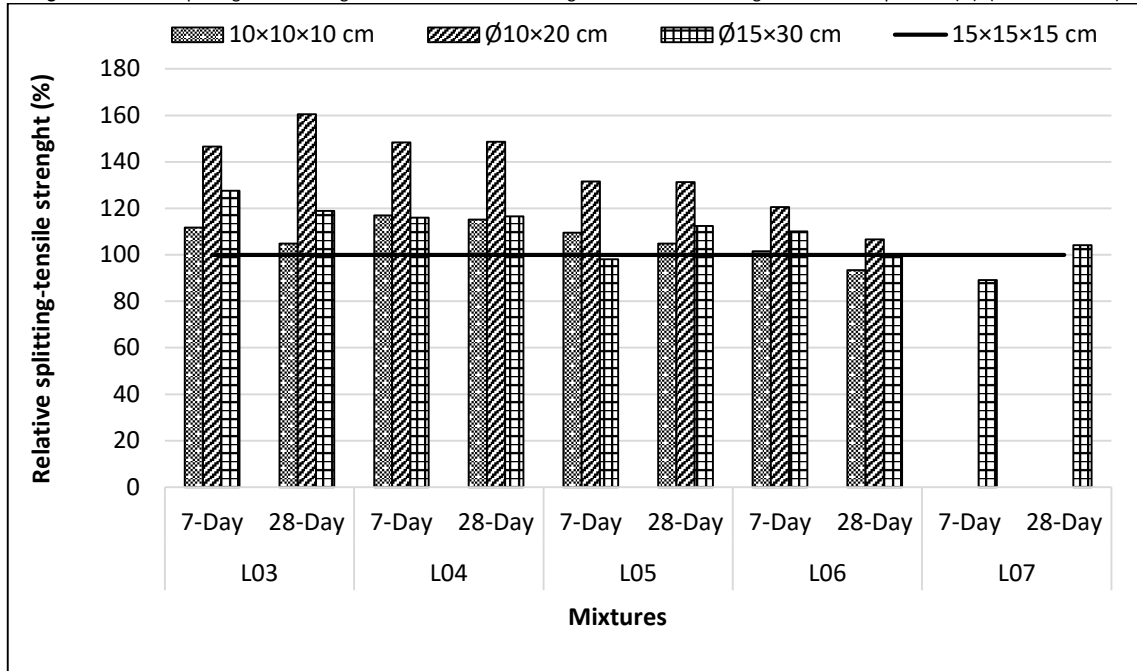

According to the TS EN 206-1 (TS EN 206, 2014) Standard, the ratio of 15 × 30 cm cylinder specimen to 15 cm cube specimen for low, normal and high strength concrete is stated to be between 20% and 25%. However, as stated by the experimental results performed in this study, regardless of the specimen age and size, the ratio of the cylinder specimen strength to the compressive strength of the cube specimen ranged from 5% to 20%. Therefore, contrary to the TS EN 206-1 (TS EN 206, 2014) Standard, the strength ratio between cylinder and cube mixtures increases as concrete strength increases, which advocates the studies in the literature (Felekoğlu & Türkel, 2005; Tokyay & Özdemir, 1997). As can be seen from the results, in non-fibrous mixtures, the strength values were increased as the specimen size decreased regardless of the specimen shape. That situation proves that it supports the size effect rule. Similar results were obtained by Del Viso et al. (2008) and Aslani (2013).

In fiber-containing mixtures, the compressive strength of small-sized specimens (10 cm cube and 10 × 20 cm cylinder) at a low W/C ratio was greater than that of the standard specimens (15 cm cube and 15 × 30 cm cylinder). However, a reverse situation was observed in high W/C ratios (Figure 4). In all series, the highest splitting tensile strength was observed in 10 × 20 cm cylinder specimens and the lowest splitting tensile strength was observed in cube specimens with 15 cm separation (Figure 5 and Figure 6). As seen in Figure 9, the compressive strength ratio of 10 cm cube specimens to 15 cm cube specimens in 7-day was 106% to 113% and in 28-day 103% to 109%. At lower W/C ratios, this phenomenon became even more obvious. The ratio of 10 × 20 cm cylinder specimens to 15 cm cube specimens was 110% and 102% in K03 mixture for 7 and 28-day specimens, respectively. In other non-fibrous mixtures, this ratio was observed to range from 85% to 97%. With the increase of concrete strength, the compressive strength of 10×20 cm cylinder concrete specimens increased slightly compared to the 15 cm cube specimens.

However, the compressive strength of 10×20 cm cylinder specimens was lower than the 15 cm cube specimens in normal and low strength concrete. It is seen that the ratio of compressive strength of standard cylinder specimen with dimensions of 15 × 30 cm to the strength of standard cube specimens of 15 cm is between 82% and 95%. These ratios increased with the increase of concrete strength. Similar results were obtained by other researchers (Ashkari, 2015; Çopuroğlu, 2001). As it seen in Figure 8, the compressive strength ratio of 10 cm cube specimens in fibrous mixtures compared to 15 cm cube specimens was between 100% and 108% for 7-day specimens and 104% to 109% for 28-day specimens. As a result, the compressive strength of fibrous cube specimen was less affected by the specimen size than non-fibrous cube specimens. As emphasized earlier, excessive wall effect was observed in 10 cm cube and 10 × 20 cm cylinder specimens in L07 mixture with a W/C ratio of 0.7 containing 1% fiber. This situation is clearly understood from Figure 11. Therefore, the strength values of these specimens could not be measured. It is thought to be due to the lack of sufficient binder and fine material in the L07 mixture.

In these mixtures, 60% of the total aggregate is used with coarse aggregate including the largest grain diameter of 22 mm and steel fiber as 1% of its total volume. For this reason, especially in the case of small specimen sizes, it became impossible to properly compress the mixture and to distribute the fiber beads uniformly. Due to the insufficient binding

material between the aggregate grains and the inner surface of the mold, the surrounding of the coarse aggregate could not be covered by the matrix. Therefore, the wall effect shown in Figure 13 occurred.

It was determined in the previous studies that the fine aggregate content should be increased by 10% in order to place the 10 cm cube concrete specimen made from the aggregate with the largest grain diameter of 19 mm according to the larger specimens in the mold by full compression (Neville A.M, 1995). Results prove that the use of small sized specimens in fibrous concrete was not appropriate. The strength ratio of the 10×20 cm cylinder specimens to 15 cm cube specimens in fibrous mixtures was between 78% -97% and 76% -100% for 7 and 28-day specimens, respectively. With the increase in concrete strength class, the strength of 10 × 20 cm cylinder specimens increased compared to 15 cm cube specimens. The compressive strength of 15×30 cm standard cylinder samples in fibrous mixtures is seen to be between 80% and 94% of the 15 cm standard cube samples. These ratios increased with the increase of the concrete strength. It was found out that these ratios are very close to each other in fibrous and non-fibrous mixtures with increasing compressive strength.

**Figure 13.** The wall effect of the 10 cm separated cubes and  $\varnothing 10 \times 20$  cm cylindrical specimens prepared with L07 mixtures. (Self-Elaboration).



As it shown in Figure 11, the splitting tensile strength ratio of 10 cm cube specimen to 15 cm cube specimen in non-fibrous mixtures is between 102% and 112% except the K04 mixture. In the study conducted by Tuğal and Arıcı (2011), it was determined that the splitting-tensile strength increased with the reduction of the specimen size. The splitting tensile strength ratio of 10×20 cm concrete specimens to 15 cm concrete specimens was found to be between 106% and 147%. This ratio was found to be higher in low strength concrete. The splitting-tensile strength ratio of 15×30 cm cylinder specimens to 15 cm cube specimens was observed between 100% and 134%. As shown in Figure 12, the fiber-tensile strength of 10 cm cube specimens in fibrous mixtures was found to be between 93% and 115% of 15 cm cube specimens. Splitting-tensile strength of 10 cm cube specimens with low W/C was higher than that of 15 cm cube specimen. However, that ratio reduces with high W/C ratio and low binding material.

This situation is thought to be due to the wall effect (Çopuroğlu, 2001). The splitting-tensile strength of 10×20 cm cylinder specimens was found to be between 107% and 161% of 15 cm specimens. The splitting-tensile strength of 15×30 cm cylinder specimens was found to be between 89% and 128% of 15 cm specimens.

#### **Relationship between the compressive and splitting-tensile strengths**

The ratio of the compressive strength to the splitting tensile strength of the specimens is summarized in Table 9 including fibrous and non-fibrous mixtures for all W/C ratios. In addition, the splitting-tensile strength results independent from the W/C ratio in the mixture is given in Table 9.

**Table 9.** Compressive strength ratio of the 7 and 28-day splitting-tensile strength of different cube and cylinder specimens. (Self-Elaboration).

Mixture code	$\sigma_{b15} / \sigma_{t15}$		$\sigma_{b15 \times 30} / \sigma_{t15 \times 30}$		$\sigma_{b10} / \sigma_{t10}$		$\sigma_{b10 \times 20} / \sigma_{t10 \times 20}$	
	7-Day	28-Day	7-Day	28-Day	7-Day	28-Day	7-Day	28-Day
K03	16.44	16.51	12.13	12.79	16.55	18.71	13.94	13.37
K04	16.43	14.05	11.78	12.58	18.19	20.53	11.66	12.46
K05	14.13	14.72	10.34	10.23	14.38	16.44	11.04	10.31
K06	13.06	14.39	9.76	10.67	13.14	15.55	8.96	8.67
K07	11.68	13.81	7.35	8.76	11.76	14.38	7.71	8.11
Average	14.35	14.70	10.27	11.01	14.80	17.12	10.66	10.58
L03	12.62	12.75	8.89	10.06	12.22	12.93	8.36	7.96
L04	12.57	12.04	9.49	8.08	11.2	11.41	7.52	6.67
L05	10.72	10.47	9.21	7.96	10.09	10.9	7.09	7.56
L06	9.81	9.4	7.7	8.48	9.69	10.48	6.36	6.67
L07	9.6	9.39	7.09	7.93	-	-	-	-
Average	11.06	10.81	8.48	8.50	10.8	11.43	7.33	7.22

According to the results in Table 9, the ratio of compression strength/splitting-tensile strength increased with the increasing of compressive strength of concrete mixture independently from the fiber usage and specimens shape. Similar results were obtained from the study conducted by Çopuroğlu (2001). The ratio of compressive strength to splitting tensile strength was found to be 14.5 for 15 cm cube specimens in non-fibrous mixtures, and 10.6 for 15×30 cm cylinder specimens. The ratios for 10 cm cubes and 10×20 cm cylinders are 15.96 and 10.62, respectively. As a result, the ratio of compressive strength to the splitting tensile strength was higher in cube specimens than in cylindrical specimens regardless of the fiber use. In addition, it is understood from Table 9 that regardless of the concrete strength class, in non-fibrous mixtures, the ratio of compressive strength / splitting-tensile strength is higher than the fibrous mixture.

The ratio of compressive strength to the splitting tensile strength in fibrous mixtures was found to be 10.94 in 15 cm cube specimens and 8.49 in 15×30 cm cylinder specimens, respectively. Likewise, for 10 cm cube and 10×20 cm cylinder specimens, this ratio was found to be 11.12 and 7.27, respectively. According to the results obtained, the findings related to the splitting-tensile and compressive strengths are as follows:

- Regardless of the use of the steel fiber and the shape of the specimen, the ratio of compressive strength / splitting-tensile strength increased with the increasing of concrete strength class.
- In non-fibrous mixtures, the ratio of the compressive strength of 15 cm cube specimen to the splitting tensile strength was 35% higher than that of 15×30 cm cylinder specimens. It has been seen that the ratio of compressive strength/splitting-tensile strength was approximately 50% higher in 10 cm cube specimens than 10×20 cm cylinder specimens.
- In fiber-containing blends, the ratio of compressive strength / splitting-tensile strength of 15 cm cube specimens was 29% higher than 15×30 cm cylinder specimens. This ratio was found to be 53% higher in 10 cm cube specimens than 10×20 cm cylinder specimens.
- It was understood from the test results that the ratio of compressive strength / splitting-tensile strength of 15 cm cube specimens was 32% higher in non-fibrous mixtures than fibrous mixtures. This ratio was determined as 43%, 26% and 46% for 10 cm cube, 15×30 cm cylinder and 10×20 cm cylinder specimens, respectively.

Regardless of the specimen size, the relationship between the splitting-tensile compressive strength of the cylinder and the cube specimens is demonstrated in Figures 14 and 15 for non-fibrous and fibrous conditions, respectively.

Figure 14. Relationship between the splitting tensile and compressive strength of the cube and cylinder specimen of non-fibrous mixtures. (Self-Elaboration).


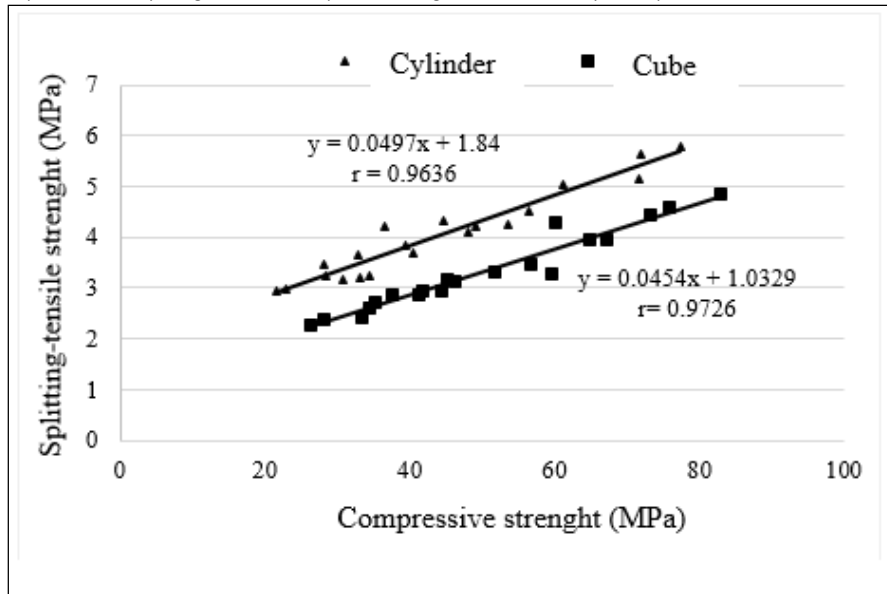


Figure 15. Relationship between the splitting tensile and compressive strength of the cube and cylinder specimens of fibrous mixtures. (Self-Elaboration).

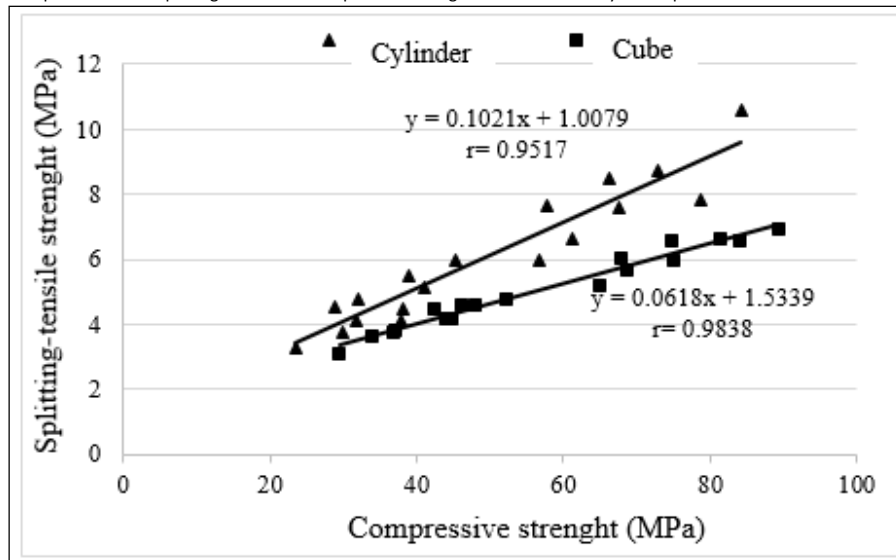

It is also understood from Figures 14 and 15 that there is a strong linear relationship between compressive and splitting-tensile strengths regardless of the fiber use and specimen shape. This behavior in cube specimens was more distinct than the cylinder specimens.

### The effect of the use of steel fiber on the strength of concrete specimens

The strength of the mixtures with 1% steel fiber and non-fibrous mixtures with the same W/C ratio is given in Table 10 and 11, respectively.

Table 10. Compressive strength ratio of the fibrous mixtures compared to non-fibrous mixtures (%). (Self-Elaboration).

Specimens (cm)	Curing time (Day)	L03/K03	L04/K04	L05/K05	L06/K06	L07/K07
10×10×10	7	111	114	102	98	0
	28	108	111	101	99	0
15×15×15	7	116	114	107	105	112
	28	111	114	104	102	102
10×20	7	102	117	96	88	0
	28	109	117	100	87	0
15×30	7	110	118	114	104	108
	28	110	114	104	110	106

**Table 11.** Splitting-tensile strength ratio of the fibrous mixtures compared to non-fibrous mixtures (%). (Self-Elaboration).

Specimens (cm)	Curing tim (Day)	L03/K03	L04/K04	L05/K05	L06/K06	L07/K07
10×10×10	7	150	184	145	134	0
	28	143	166	144	143	0
15×15×15	7	151	149	142	139	136
	28	143	133	146	157	150
10×20	7	170	182	150	124	0
	28	183	187	138	113	0
15×30	7	150	147	128	131	112
	28	139	156	134	138	117

As shown in Table 10 and 11, 15 cm cube specimens, the compressive strength of fibrous mixture was 102% and 117% of compressive strength of non-fibrous mixtures and this ratio in splitting-tensile strength was 133-157%. Similarly, an increase of 99% to 114% in compressive strength of fibrous mixtures was observed. This ratio for splitting-tensile strength was 143% to 166% of non-fibrous mixtures. In the 15×30 cm cylinder specimens, an increase of 104% to 114% was observed in the compressive strength values of fibrous mixtures compared to non-fibrous mixtures, while an increase of 134 to 156% in spitting-tensile strength was recorded. According to the results, no significant effect of the use of steel fiber on the compressive strength of low and normal strength concrete was observed. In specimens with small size (10 cm cube, 10 × 20 cm cylinder) and with high W / C ratio, decrease in the compressive strength of fibrous concrete mixtures was observed.

The compressive strength of the mixture with W / C ratio of 0.7 could not be measured due to the excessive wall effect on the specimens. This is thought to be due to the fact that the binder material and fine aggregate are small and that the fibers do not homogeneously disperse in the mixture and thus lead to agglomeration. Therefore, the use of small-sized specimens in low-strength fibrous concretes was not suitable. Similar behaviors were observed in the splitting tensile strength of the concrete mixtures. With the use of fiber, the spitting-tensile strength of the concrete mixtures was increased between 1.12 and 1.87. However, as observed in the measurement of the compressive strength of concrete mixtures, the splitting-tensile strength of small-sized specimens prepared at a W / C ratio of 0.7 could not be measured. However, with the use of fiber in high-strength concrete, a 10% increase in compressive strength of the concrete mixtures was determined.

## Conclusions

The results summarized below were obtained based on the materials used and in accordance with the methods applied.

- As expected, the strength of concrete mixtures increased over time, regardless of the specimen shape, size and fiber utilization.
- In the concrete with low W/C ratio, the first 7-day strength development was faster than the mixtures with high water / cement ratios.
- 85% of the 28-day compressive strength was gained in the first 7 days.
- As expected, the strength of the concrete mixtures increased with the reduction of W/C ratio, regardless of fiber use, specimen size and shape.
- It has been observed that with the increase in concrete strength class, the strength ratio between cylinder and cube specimen has increased.
- In non-fibrous mixtures, strength values were increased as the specimen size decreased, regardless of the specimen shape.
- In the fiber-containing mixtures, compared to the standard specimens (15 cm cubes and 15×30 cm cylinders), the small specimens (10 cm cubes and 10 × 20 cm cylinders) showed better performance in terms of compressive strength. However, in the case of high w/c ratio, the compressive strength decreased compared to the standard specimens owing to the existence of wall effect in small size specimens. In this context, the strength values of the small-sized fibrous specimens with a W/C ratio of 0.7 could not be measured because of the excessive wall effect in the specimen. Therefore, small size specimens do not exhibit real behavior in terms of strength in fiber-containing mixtures with high W/C ratio.
- It was found that the compressive strength of fiber-containing cube specimen was less affected by specimen size than non-fibrous cube specimens.
- Regardless of fiber usage and specimen shape, an increase was observed in the compressive strength/splitting tensile strength ratio with the compressive strength increase of the concrete mixture.

- Regardless of the steel fiber use, the ratio of compressive strength to splitting-tensile strength in cubic specimens was higher than that of cylindrical specimens. Furthermore, it was found that, in fiber-free mixtures, compressive strength/ splitting-tensile strength ratio was higher than the fiber containing mixtures, regardless of the concrete strength class.
- Regardless of the steel fiber usage and specimens shape, a strong linear relationship was found between compressive and splitting-tensile strengths. This behavior in cube specimens was more distinct than the cylindrical specimens.
- It was observed that the use of steel fiber has no significant effect on the compressive strength of the concrete with low and normal strength class. However, with the use of fiber in high strength concrete, a 10% increase in compressive strength of concrete mixtures was determined.



- Aitcin, P. C., Miao, B., Cook, W. D., & Mitchell, D. (1994). Effects of size and curing on cylinder compressive strength of normal and high-strength concretes. *ACI Materials Journal*, 91(4), 349–354. <https://doi.org/10.14359/4044>
- Alex, X. I., & Arunachalam, K. (2019). Flexural behavior of fiber reinforced lightweight concrete. *Revista de La Construcción*, 18(3), 536–544. <https://doi.org/10.7764/RDLC.18.3.536>
- Ashkari, H. (2015). Effect of geometry of concrete specimen on compressive strength [Master Theses, Ege University, Graduate School of Natural and Applied Sciences, P 115]. <https://tez.yok.gov.tr/>
- Aslani, F. (2013). Effects of specimen size and shape on compressive and tensile strengths of self-compacting concrete with or without fibres. *Magazine of Concrete Research*, 65(15), 914–929. <https://doi.org/10.1680/mac.13.00016>
- CEB-FIP MC10. (2010). Model Code 2010. In fib Model Code for Concrete Structures 2010. <https://www.fib-international.org/>
- Che, Y., Ban, S. L., Cui, J. Y., Chen, G., & Song, Y. P. (2011). Effect of specimen shape and size on compressive strength of concrete. In *Advanced Materials Research* (Vol. 163, pp. 1375-1379). Trans Tech Publications Ltd.
- Çopuroğlu, O. (2001). Specimen size and shape effect on compressive and tensile strength of concrete [Ege University]. <https://tez.yok.gov.tr/>
- Dehestani, M., Nikbin, I. M., & Asadollahi, S. (2014). Effects of specimen shape and size on the compressive strength of self-consolidating concrete (SCC). *Construction and Building Materials*, 66, 685–691. <https://doi.org/10.1016/j.conbuildmat.2014.06.008>
- Del Viso, J. R., Carmona, J. R., & Ruiz, G. (2008). Shape and size effects on the compressive strength of high-strength concrete. *Cement and Concrete Research*, 38(3), 386–395. <https://doi.org/10.1016/j.cemconres.2007.09.020>
- Felekoğlu, B., & Türkel, S. (2005). Effects of specimen type and dimensions on compressive strength of concrete. *Journal of Science*, 18(4), 639–645.
- Gyurkó, Z., & Nemes, R. (2020). Specimen size and shape effect on the compressive strength of normal strength concrete. *Periodica Polytechnica Civil Engineering*, 64(1), 276–286. <https://doi.org/10.3311/PPci.15338>
- Khalilpour, S., & Dehestani, M. (2021). Enhanced specimen size and shape effect models for high-strength fibre-reinforced concrete. *Proceedings of the Institution of Civil Engineers - Structures and Buildings*, ISSN 0965-0911, 1–16. <https://doi.org/10.1680/jstbu.19.00086>
- Köroglu, M. A., & Ashour, A. (2019). Mechanical properties of self-compacting concrete with recycled bead wires. *Revista de La Construcción*, 18(3), 501–512. <https://doi.org/10.7764/RDLC.18.3.501>
- Li, M., Hao, H., Shi, Y., & Hao, Y. (2018). Specimen shape and size effects on the concrete compressive strength under static and dynamic tests. *Construction and Building Materials*, 161, 84–93. <https://doi.org/10.1016/j.conbuildmat.2017.11.069>
- Mardani-Aghabaglou, A., İlhan, M., & Özen, S. (2019). The effect of shrinkage reducing admixture and polypropylene fibers on drying shrinkage behaviour of concrete. *Cement, Wapno, Beton*, 24(3), 227–238. <https://doi.org/10.32047/CWB.2019.24.3.227>
- Neville A.M. (1995). Properties of Concrete. In British library cataloguing in publication data (Fourth edi). Pearson education limited.
- Ouedraogo, H. A., Özen, S., Kobya, V., Sagioglu, S., & Mardani-Aghabaglou, A. (2021). Comparison of fresh and hardened properties of self-compacting concrete mixture from different aspect ratio of steel fiber view point. *Journal of Green Building*, 16(1), 115–138. <https://doi.org/10.3992/jgb.16.1.115>
- Tokyay, M., & Özdemir, M. (1997). Specimen shape and size effect on the compressive strength of higher strength concrete. *Cement and Concrete Research*, 27(8), 1281–1289. [https://doi.org/10.1016/S0008-8846\(97\)00104-X](https://doi.org/10.1016/S0008-8846(97)00104-X)
- TS EN 1097-6. (2013). Tests for mechanical and physical properties of aggregates- Part 6: Determination of particle density and water absorption. <https://intweb.tse.org.tr/>
- TS EN 12350-2. (2010). Testing fresh concrete- Part 2: Slump test. <https://intweb.tse.org.tr/>
- TS EN 14889-1. (2006). Fibres for concrete - Part 1: Steel fibres - Definitions, specifications and conformity. <https://intweb.tse.org.tr/>
- TS EN 197-1. (2012). Cement- Part 1: Compositions and conformity criteria for common cements. <https://www.scribd.com/>
- TS EN 206. (2014). Concrete- Part 1: Specification, performance, production and conformity. <https://intweb.tse.org.tr/>
- Tuğal, M., & Arıcı, E. (2011). Investigate of size effect in geometric changes of splitting tensile strength of concrete. *E-Journal of New World Sciences Academy*, 6(4), 1086-1092. [https://dergipark.org.tr/Yi, S.-T., Yang, E.-I., & Choi, J.-C. \(2006\). Effect of specimen sizes, specimen shapes, and placement directions on compressive strength of concrete. \*Nuclear Engineering and Design\*, 236\(2\), 115–127. <https://doi.org/10.1016/j.nucengdes.2005.08.004>](https://dergipark.org.tr/Yi, S.-T., Yang, E.-I., & Choi, J.-C. (2006). Effect of specimen sizes, specimen shapes, and placement directions on compressive strength of concrete. Nuclear Engineering and Design, 236(2), 115–127. https://doi.org/10.1016/j.nucengdes.2005.08.004)
- Zeynal, E. (2008). The effect of steel fiber and w / c ratios on impact strength and mechanical properties of steel fiber concretes [Ege Univeristy]. <https://tez.yok.gov.tr/>
- Zhang, Y., Li, H., Abdelhady, A., Yang, J., & Wang, H. (2021). Effects of specimen shape and size on the permeability and mechanical properties of porous concrete. *Construction and Building Materials*, 266, 121074. <https://doi.org/10.1016/j.conbuildmat.2020.121074>